


(a) 20°C curing temperature

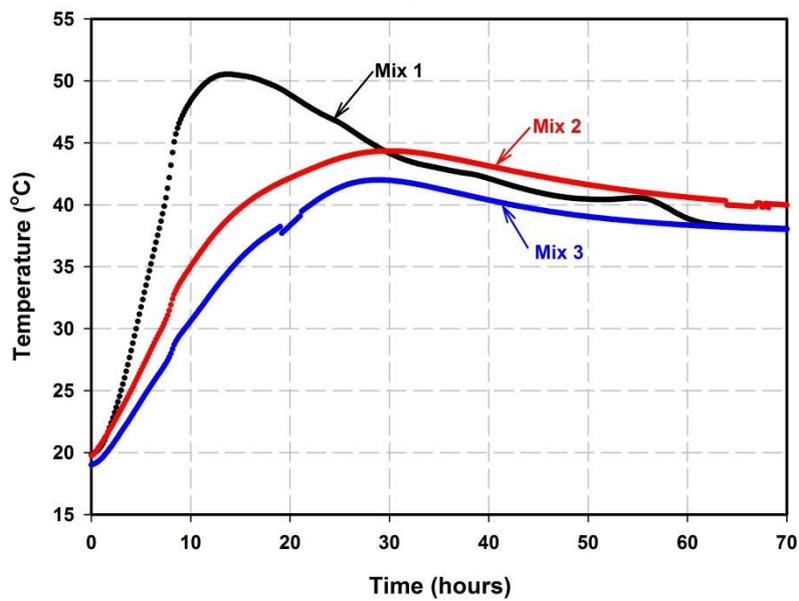

(b) 38°C curing temperature

Figure 3: Temperature in the centre of slab specimens

Table 5: T1 values in the core of 300mm slab specimens

	T1 (°C)	
	20°C curing temperature	38°C curing temperature
Mix 1: 100% CEM I	10.4	12.5
Mix 2: 50% GGBS	3.3	6.3
Mix 3: 70% GGBS	4.1	4.0

Partial replacement of CEM I with GGBS has a detrimental effect on the early-age strength of concrete under a standard curing temperature of 20°C. The 3-day compressive strengths of GGBS concrete mixes, i.e. Mix 2 and 3, were lower than that of Concrete Mix 1, **Figure 4**. This detrimental effect was found to be less significant at a higher curing temperature. The average 3-day compressive strength of Mix 2 was 24.0N/mm² which was very similar to that of Mix 1, 24.9N/mm², at 38°C curing temperature.

A high curing temperature however has a detrimental effect on the 28-day strength of concrete. The average 28-day compressive strengths of Mix 1 reduced from 46.4N/mm² to 42.2N/mm² when the curing temperature was increased from 20°C to 38°C, **Figure 4**. This detrimental effect however became less significant when 50% CEM I was replaced with GGBS. This indicates the strength of GGBS concrete was less adversely affected by the high temperature curing compared to CEM I mixes and this finding agrees with Barnett (Barnett et al., 2006) and Wang (Wang et al., 2012).

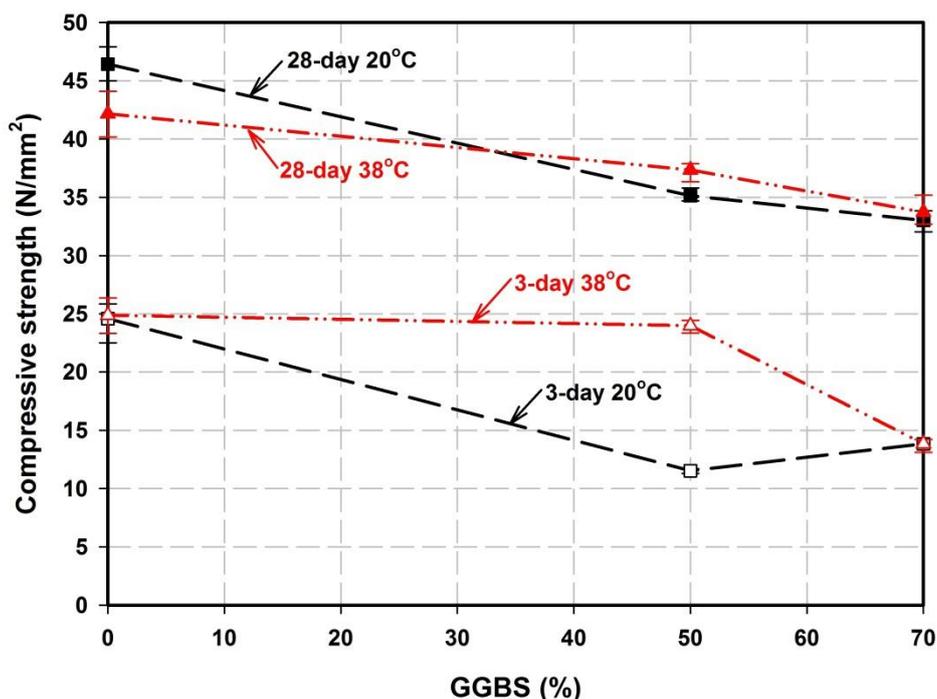


Figure 4: Compressive strengths at 3 and 28 days

4. CONCLUSIONS

Partial replacement of CEM I with GGBS contributes to a reduction in the peak hydration temperature. This has a beneficial effect on hot weather concreting. GGBS concrete has a lower early-age strength compared to CEM I concrete and this may cause a premature tension failure in long-span concrete structures. On the other hand,

early-age strength of GGBS concrete is improved by high curing temperatures. More GGBS concrete mixes will be conducted to identify an 'optimum' replacement level which will balance these factors. A case study investigation will also be conducted to investigate the potential economic benefit through using GGBS in high value markets such as the replacement of cement in long-span concrete structures to reduce the requirement for thermal crack control reinforcement.

REFERENCES

- ACI Committee 305 (1999). *Hot weather concreting*. ACI.
- Bamforth, P. B. (2007). *CIRIA C660 Early-age Thermal Crack Control in Concrete*. London: CIRIA
- Barnett, S. J., M. N. Soutsos, S. G. Millard & J. H. Bungey (2006). Strength development of mortars containing ground granulated blast-furnace slag: Effect of curing temperature and determination of apparent activation energies. *Cement and Concrete Research* 36: 434-40.
- Bougara, A., J. Khatib & H. Khellafi (2009). Some parameters affecting the heat of hydration of blast-furnace slag cement. *1st International Conference on Sustainable Built Environment Infrastructures in Developing Countries*. ENSET Oran, Algeria.
- BSI (2006). *BS 8500-1: 2006 Complementary British Standard to BS EN 206-1. Method of specifying and guidance for the specifier* British Standards Institution (BSI) London.
- Chinese State Council (2013). *The guidance on the overcapacity of industries*.
- da Silva, W. R. L., V. milauer & P. temberk (2013). Upscaling semi-adiabatic measurements for simulating temperature evolution of mass concrete structures. 1-11.
- Dhir, R. K., K. A. Paine & L. Zheng (2006). *Design data for use where low heat cements are used DTI Research Contract No. 39/680, CC2257. Report No CTU 2704*. University of Dundee.
- GB (2008). *GB/T 18046-2008 Ground granulated blast furnace slag used for cement concrete*. General administration of quality supervision, inspection and quarantine of the People's Republic of China.
- Kim, G.-Y., E.-B. Lee, J.-S. Nam & K.-M. Koo (2011). Analysis of hydration heat and autogenous shrinkage of high-strength mass concrete. *Magazine of Concrete Research* 63: 377-89.
- Koenders, E. A. B., M. Pepe & E. Martinelli (2014). Compressive strength and hydration processes of concrete with recycled aggregates. *Cement and Concrete Research* 56: 203-12.
- Paine, K. A., L. Zheng & R. K. Dhir (2005). Early-Age Temperature Rises in GGBS Concrete - Part 2: T1 Values for Low Heat and Very Low Heat Cements. In Dhir, R. K., T. A. Harrison & M. D. Newlands (eds.) *International Congress - Global Construction: Ultimate Concrete Opportunities*. London, Thomas Telford. 183-94.

- Tang, K., S. Millard & G. Beattie (2013). Technical and economic aspects of using GGBFS for crack control mitigation in long span reinforced concrete structures. *Construction and Building Materials* 39: 65-70.
- Wang, Q., M. Miao, J. Feng & P. Yan (2012). The influence of hightemperature curing on the hydration characteristics of a cement-GGBS binder. *Advances in Cement Research* 24: 33-40.
- Zhang, J., H. Liu & X. Hu (2001). High-grade compound cement production with large amount of fly ash. *Cement* 3: 46.
- Zheng, L., K. A. Paine & R. K. Dhir (2005). Early-Age Temperature Rises in GGBS Concrete: Part 1: Determination of T1 Values. In Dhir, R. K., T. A. Harrison & M. D. Newlands (eds.) *International Congress - Global Construction: Ultimate Concrete Opportunities*. London, Thomas Telford. 173-82.