

Table 2D Scaled contributions (relative variance contributions) [%]

Variable ID	F1	F2	F3
Var1 (Length)	0.1	74.8***	0.0
Var2 (Diameter)	9.3	22.9***	0.0
Var3 (Aspect ratio)	37.5***	0.3	0.3
Var4 (FIER)	37.9***	0.4	0.1
Var5 (Hook geometry)	2.7	0.5	41.9
Var6 (Tensile strength)	12.0	0.1	0.7
Var7 (Ductility)	0.4	1.0	57.0***

The detailed contribution of all variables to the main PCA factors is presented in **Table 2B** (most important according to contribution of the variables criterion were marked as bold and labelled with asterisk). To inspect more strictly the PCA factors in terms of the relevant variables the squared cosines of the variables and scaled contributions (relative variance contributions) were calculated and presented in **Tables 2C** and **2D**, respectively. For variables 4 and 5 (F1 column) the squared cosines are greater than 0.5. According to such criterion (**David & Jacobs 2014**), the real correlation may exist and these variables strongly contribute for PCA factor F1 (appropriate numbers are marked as bold and labelled as double asterisks within **Table 2C**).

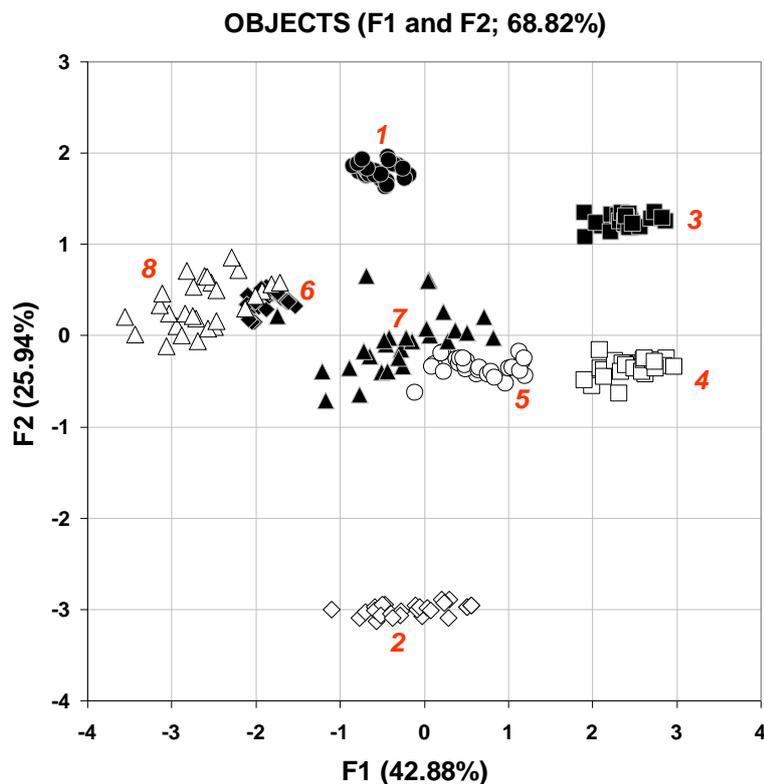


Fig. 7 Principal component plot showing objects clustering (all individual steel fibres) in two dimensional space (F1 and F2 factors scores) - numbers from 1 to 8 are related to particular types of engineered steel fibres (see **Table 1**)

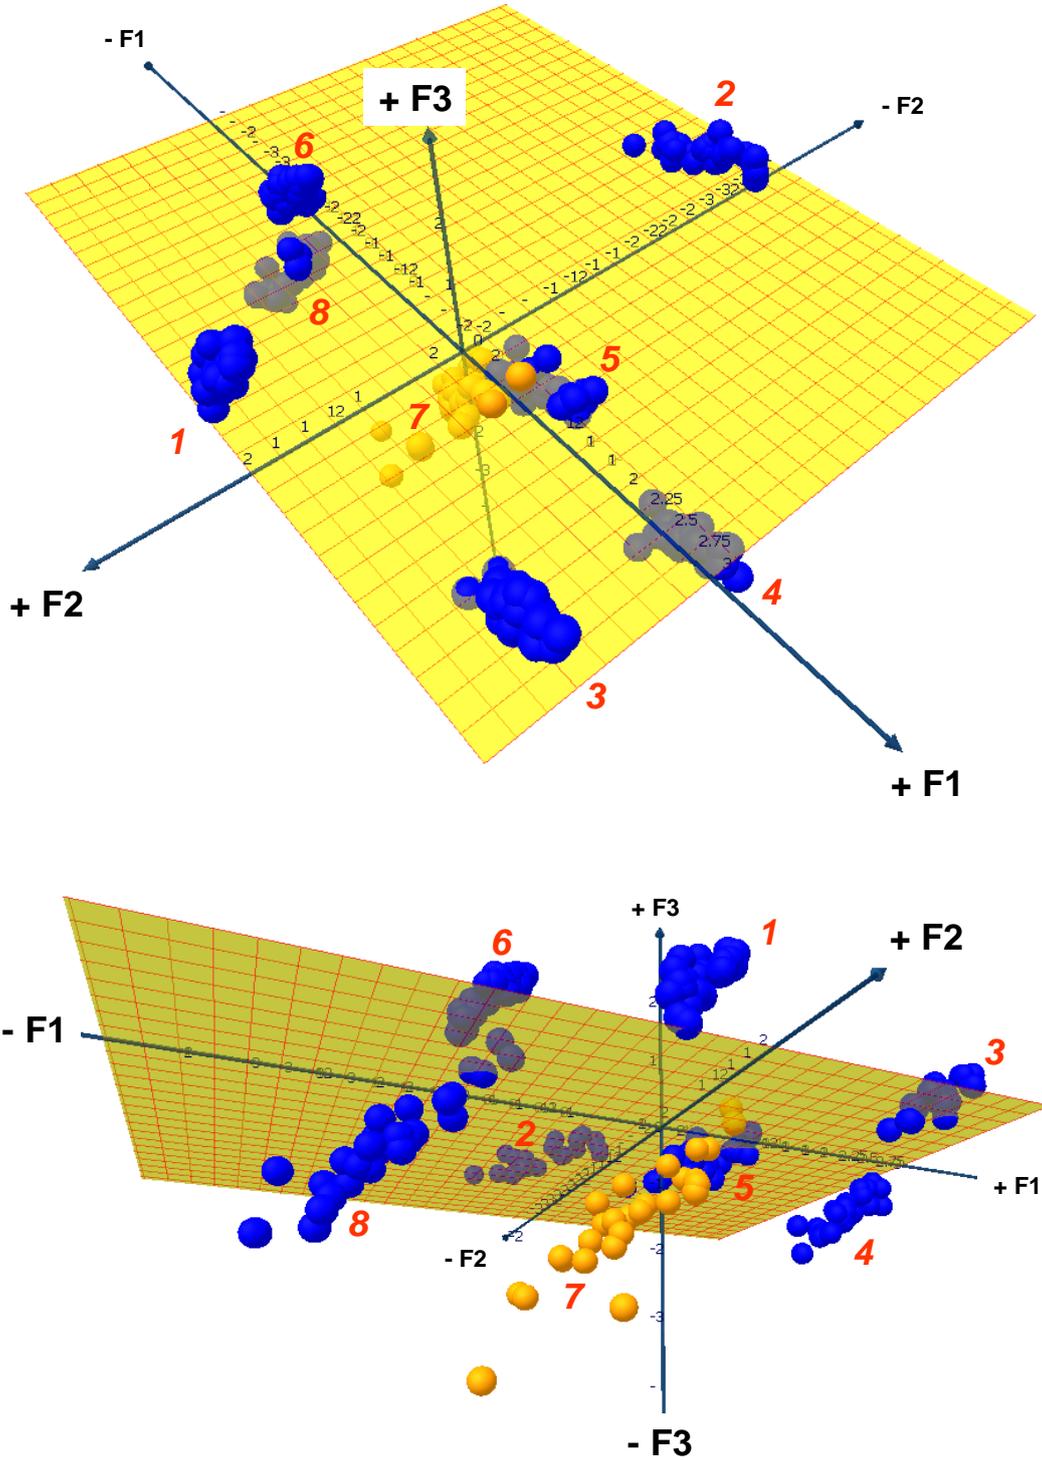


Fig. 8. Principal component plot showing relationships between objects investigated (all individual steel fibres) in three dimensional space (F1, F2 and F3 factors scores). Numbers from 1 to 8 are related to particular types of engineered steel fibres (Table 1)

Considering scaled contributions values (Table 2D) related to the first PCA factor, the variables 3 and 4 are responsible for 75.4% of information included in F1 (sum of data bolded and labelled as triple asterisks within F1 column). In case of PCA factor F2 the squared cosines and scaled contributions data confirm the analysis based on the factor loadings (Table 2A) and contribution of the variables (Table 2B) criteria. Basically, the fibres length (variable 1) and diameters (variable 2) are strongly contributing to F2. Nevertheless, considering data included in Tables 2C and 2D the ductility (variable 7) should be considered as the main variable contributing to PCA factor F3.

The principal component plot showing objects (individual fibres) clustering is presented in Fig. 7. According to data presented in the principal component plot, information that persists in studied mechanical and spatial parameters is sufficient for accurate fibres classification using the multivariate approach. As it may be observed, this technique allows precise classification of individual fibres taking into account two dimensional space, involving factors F1 and F2. Complete clusters separation (including fibre types 6, 8 and particularly 5 and 7) can be performed considering three factors simultaneously, due to their location in three dimensional factor scores space (Fig. 8). Observed on these PCA graphs individual steel fibres clustering and significant separation between clusters related to particular types of the fibres, strongly supports the hypothesis that parameters selected in this study contain key and almost complete information that may reveal the important differences between steel fibre types. Nevertheless, the calculations should be repeated using additional parameters such as pull-out strength etc. There is also a need to find new parameters describing, more precisely, properties of steel fibre that may improve accurate classification of such objects using multivariate computations. PCA factors, proposed in this study, may occur very valuable for modelling fibre reinforced concrete and identification of its properties (Sucharda et al. 2015).

4. CONCLUSIONS

Presented research has revealed that direct comparison of engineered steel fibres used as reinforcement for concrete *via* univariate approach may be strongly limited. It became clear that properties of tested fibre populations were significantly differentiated. Due to the nature of parameters commonly used for their steel fibre characterization, resulting quantitative data may be treated as multivariate data set. The applied in this research multivariate approach enables easy comparison of the parameters (variables) and to classify individual fibres for given type of engineered steel fibre. Utilized PCA calculations indicated that length/diameter ratio and FIER parameters may carry equal information in case of the fibres that are characterized by similar cross-section shape. The calculations should be repeated using additional parameters such as pull-out strength etc. The achieved results proved that there is a need of finding new parameters describing, more precisely, properties of steel fibre. New parameters may improve accurate classification of steel fibre such objects using multivariate computations.

REFERENCES

- Colajanni, P., Recupero, A. and Spinella, N. (2012), "Generalization of shear truss model to the case of SFRC beams with stirrups", *Computers and Concrete*, **9** (3), 227-244.
- Corder, G.W. and Foreman, D.I. (2009), *Nonparametric Statistics for Non-Statisticians: A Step-by-Step Approach*, Wiley, New Jersey, USA.
- David, C.C. and Jacobs, D.J. (2014), "Principal Component Analysis: A Method for Determining the Essential Dynamics of Proteins", *Methods Mol Biol*, 1084.
- Domski, J. (2016), "A blurred border between ordinary concrete and SFRC", *Construction and Building Materials*, **112**, 247-252.
- Ellison, S.L.R. et al. (2009), *Practical Statistics for the Analytical Scientist: a Bench Guide*, LGC Ltd., Cambridge, UK.
- EN ISO 6892-1:2009. *Metallic materials -- Tensile testing -- Part 1: Method of test at room temperature*.
- EN 10218-1:1994. *Steel wire and wire products. General. Test methods*.
- EN 14889-1:2009. *Fibres for concrete - Part 1: Steel fibres - Definitions, specifications and conformity*.
- Ghorpade, V.G. and Sudarsana Rao, H. (2010), "Strength and permeability characteristics of Fibre reinforced recycled aggregate concrete with different fibres", *Nature Environment and Pollution Technology* **9**, 179-188.
- Havlikova, I. et al. (2015), "Effect of Fibre Type in Concrete on Crack Initiation", *Applied Mechanics and Materials* **769**, 308-311.
- Jian-bo Chen, Su-qin Sun and Qun Zhou (2015), "Data-driven signal-resolving approaches of infrared spectra to explore the macroscopic and microscopic spatial distribution of organic and inorganic compounds in plant", *Anal Bioanal Chem* **407**, 5695-5706.
- Katzer, J. and Domski, J. (2012), "Quality and mechanical properties of engineered steel fibres used as reinforcement for concrete", *Constr Build Mater* **34**, 243-248.
- Katzer, J. and Domski, J. (2013), "Optimization of fibre reinforcement for waste aggregate cement composite", *Construction and Building Materials* **38**, 790-795.
- Kim, D.J. et al. (2008), "Loading Rate Effect on Pullout Behavior of Deformed Steel Fibers", *ACI Materials Journal*, November-December 2008, 576-584.
- Maidl, B.R. (1995), *Steel Fibre Reinforced Concrete*, Ernst & Sohn, Berlin, Germany.
- Naaman, A.E. (2003), "Engineered Steel Fibres with Optimal Properties for Reinforcement of Cement Composites", *Journal of Advanced Concrete Technology*, **1**(3), 241-252.
- Nawy, E.G. (1996), *Fundamentals of High Strength High Performance Concrete*, Longman, England.
- Neocleous, K. et al. (2011), "Fibre-reinforced roller-compacted concrete transport pavements", *ICE Proceedings Transport* **164**, 97-109.
- Pajak, M. and Ponikiewski, T. (2013), "Flexural behavior of self-compacting concrete reinforced with different types of steel fibers", *Construction and Building Materials*, **47**, 397-408.
- Pearson, K. (1901), "On lines and planes of closest fit to systems of points in space", *Philos Mag* **2**, 559-572.

- Pereira ,J.C., Azevedo, J.C.R., Knapik, H.G. and Burrows, H.D. (2016), “Unsupervised component analysis: PCA, POA and ICA data exploring - connecting the dots”, *Spectrochimica Acta Part A: Molecular and Biomolecular Spectroscopy*, **165**, 69–84.
- Pereira, J.C., Serpa, C., Arnaut, L.G. and Formosinho, S.J. (2010), “Molecular factor analysis in self-exchange electron transfer reactions in solution”, *Journal of Molecular Liquids*, **156**, 3-9.
- Perez, R.L. and Escandar, G.M. (2016), “Multivariate calibration-assisted high-performance liquid chromatography with dual UV and fluorimetric detection for the analysis of natural and synthetic sex hormones in environmental waters and sediments”, *Environmental Pollution*, **209**, 114-122.
- Ponikiewski, T. et al. (2014), “Determination of steel fibres distribution in self-compacting concrete beams using X-ray computed tomography”, *Archives of Civil and Mechanical Engineering*, DOI: 10.1016/j.acme.2014.08.008
- Soetensa, T., Van Gyselb, A., Matthysa, S. and Taerwea, L. (2013), “A semi-analytical model to predict the pull-out behaviour of inclined hooked-end steel fibres”, *Construction and Building Materials*, **43**, 253-265.
- Soroush Mohammadzadeh, Yeesock Kim and Jaehun Ahn. (2015), “PCA-based neuro-fuzzy model for system identification of smart structures. Smart Structures and Systems”, *An Int'l Journal*, **15**,
- Soulioti, D.V., Barkoula, N.M., Paipetis, A. and Matikas, T.E. (2011), “Effects of Fibre Geometry and Volume Fraction on the Flexural Behaviour of Steel-Fibre Reinforced Concrete”, *Strain An International Journal of Experimental Mechanics* **47**, 535-541.
- Spinella, N. (2013), “Shear strength of full-scale steel fibre-reinforced concrete beams without stirrups”, *Computers and Concrete* **11**(5), 365-382.
- Sucharda, O. et al. (2015), “Finite element modelling and identification of the material properties of fibre concrete”, *Procedia Engineering* **109**, 234-239.
- Tutmez, B. (2014), “Use of partial least squares analysis in concrete technology”, *Computers and Concrete* **13**(2), 173-185.
- Xie Jian-he, et al. (2015), “Compressive and flexural behaviours of a new steel-fibre-reinforced recycled aggregate concrete with crumb rubber”, *Construction and Building Materials* **79**, 263-272.
- Zarzycki, P.K. and Portka, J.K. (2015), “Recent advances in hopanoids analysis: quantification protocols, main research targets and selected problems of data analysis”, *J Steroid Biochem Mol Biol* **153**, 3-26.
- Zarzycki, P.K., Zarzycka, M.B., Ślącza, M.M. and Clifton, V.L. (2010), “Acetonitrile, the polarity chameleon”, *Anal Bioanal Chem* **397**, 905-908.